

The Influence of Punch Angle on the Spring Back during V- Bending of Medium Carbon Steel

by Asmeati Unifa

Submission date: 18-Apr-2023 12:57PM (UTC+0700)

Submission ID: 2068095578

File name: e_on_the_Spring_Back_during_V-Bending_of_Medium_Carbon_Steel.pdf (595.29K)

Word count: 1706

Character count: 8674

2 The Influence of Punch Angle on the Spring Back during V-Bending of Medium Carbon Steel

Muhammad Arsyad Suyuti^{1, a *}, Rusdi Nur^{1, b} and Asmeati^{2, c}

¹Politeknik Negeri Ujung Pandang, Makassar 90245, Indonesia

²Universitas Fajar, Makassar 90241, Indonesia

^amuhammad_arsyad_suyuti@yahoo.co.id, ^bar_rusdi_nur@yahoo.com, ^casmeatisabir@yahoo.co.id

*muhammad_arsyad_suyuti@yahoo.co.id

Keywords: Punch Angle, Spring back, Medium Carbon Steel, V-Bending.

2
Abstract. This study presents the influence of punch angle on the behavior of spring back for the medium carbon steel under V-bending by the experimental and analytical studies. Punch angle from 80°, 85° and 90° were applied to the samples, which were bent on a 90° V-shaped die for the spring back evaluation. The result of experiment and calculation indicates that the spring back has the similar results for the punch angles of 80°, 85° and 90°.

Introduction

12
Bending process is widely used in metal forming mainly to making products and components in the manufacturing process such as production of components for the electronic panels, car panels, tool box, leaf wheel, hand tractors, etc. As it is known that the sheet bending is one of the manufacturing processes which essential, but there are some technical problems such as predicting the causes and effects of spring back after forming [1]. The spring back is a phenomenon in which a piece of metal is not formed itself after the forming operation and it generally occur in sheet metal forming, which caused the elastic stress redistribution after the punch load is removed (unloading) [2-3]. Spring back is a condition that occurs in the plate sheet after bending process done where after the punch load is removed the bent plate sheet has a tendency to return to the original shape.

Spring back is not only affected by the tensile strength and stress but also influenced by the thickness of the plate, bending radius and angle. In addition, according to Kazan "Spring back is an important parameter in designing the equipment and obtaining the desired part geometry"[4]. Controlling spring back in bending process is applied in practice become difficult for several reasons, especially in mass production [5]. Sheet metal has been widely used in the industry and can be done by processes such as bending, stretching and drawing, but the selection of sheet materials and design tools always depend on trial and error conditions [1, 6].

15
The spring back issue has been studied over the years to compensate for the undesired shape errors to identify the influence of main factors, such as material of workpiece, tooling geometry, and process parameters, on the amount of spring back, both experimentally and numerically. Asnafi examined the influence of process parameters on the spring back in the V-bending process by developing theoretical models for stainless-steel sheets[7].

17
Therefore, the spring-back prediction was a very serious issue in sheet metal forming. The determination of accurate spring-back value in designing and making the V-bending punch is a very critical problem. In this paper, there are two ways of determining the amount of spring back in the V-bending process of medium carbon steel materials both theoretically and experimentally.

Calculation of Spring back

Spring back is a back force caused by the influence of the elasticity of plate material experiencing a process formation. The amount of back force is determined by the value of elasticity modulus in the material. In this bending process should be considered force back or spring back. Spring back occurs because of the irregularities on bending angle is formed. A simple example can be seen during the

bending process. For bending the plate with an angle 90° then required size of the angle 'V' on the die is less than 90° ($< 90^\circ$), thus the process can produce the angles of bending plate on 90° . The spring back process of bending establishment can be seen as in Figure 1.

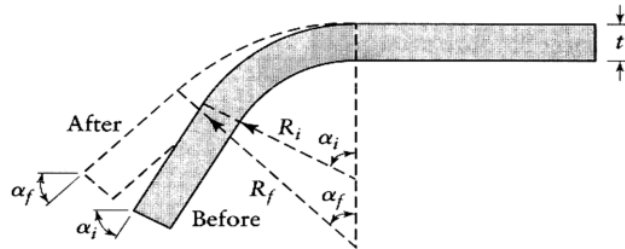


Fig. 1 Spring back in bending process [8]

In the forming process, the metal will experience changes in dimensional after loading abolished. This is caused by the elastic properties of the metal and the strain change that produced by the elastic recovery. If the load is removed, the total strain will be reduced and causing the elastic recovery. Elastic recovery effect on spring back, which could spring back increase if the yield stress is higher, or lower elastic modulus and plastic strain increases.

Spring back can be applicable to all processes of bending; in particularly most easily observation that bending results. The radius of curvature (R_i) will be smaller than the radius of curvature (R_f) after the load is removed. Spring back can be calculated using equation 1 and 2[9]:

$$K_s = \frac{\alpha_f}{\alpha_i} = \frac{(2.R_i/T)+1}{(2.R_f/T)+1} \tag{1}$$

$$\frac{R_i}{R_f} = 4 \left(\frac{R_i Y}{E T} \right) - 3 \left(\frac{R_f Y}{E T} \right) + 1 \tag{2}$$

where K_s is the factor of spring back, α_f is the angle of bend plate ($^\circ$), α_i is the punch angle ($^\circ$), R_i is the punch radius in mm, T is the thickness of plate in mm, R_f is the plate radius after bent in mm, Y is the yield strength in N/mm^2 , and E is the modulus of elasticity in MPa.

Materials and Experimental Methods

In this study, the material used was medium carbon steel shaped the plate with a thickness of 6 mm in size and had the specifications shown in Table 1. These plates would be tested by using a press tool die set which installed on the Universal Testing Machine (Galdabini Type PM 100).

Table 1. The Specification of material for V-bending

Specifications	Medium carbon steel
Maximum of tensile strength (kgf/mm^2)	57.633
Yielding strength (N/mm^2)	480.77
Elongation (%)	25.2

In the experiments, the bending test was performed for two conditions, namely the punch angle and the punch radius. The punch angle was tested in 80° , 85° , and 90° for the variation of punch radius was 2 mm, 4 mm, and 6 mm.

Results and Discussions

Based on the experiments, the bending testing was generated the spring back data as listed in Table 2, as well as the results obtained with spring back calculation which refer to Eq. 1 and 2.

Table 2. The value of spring back resulted by equation and experiment

Punch Radius(mm)	Punch Angle (°)	Die Angle(°)	Spring back (°)	
			Equation	Experiment
2	80	90	-9.97	-9.06
	85	90	-4.97	-4.72
	90	90	0.03	-0.97
4	80	90	-9.93	-9.36
	85	90	-4.92	-5.17
	90	90	0.08	-0.31
6	80	90	-9.87	-9.78
	85	90	-4.86	-3.53
	90	90	0.14	0.47

Table 2 and Figure 2 are the descriptions of the relationship between the punch and the spring back angle and it is known that the spring back that occurs for the third punch radius there are positive and some are negative. Spring back angle formed positive means more than 90° , while for negative spring back means bending angle formed less than 90° . Based on Figure 2, there are indications that the greater the angle of the punch then spring back values generated tend to be small or close to zero. These results were confirmed by Livatyalı and Altan which examined spring back can be predicted by using CAD. It was concluded that made a comparison between the analytical model and experimental results which will obtain the trend in [10] that showed good results, such as lower back spring obtained at a lower gap and also at a smaller die radius.

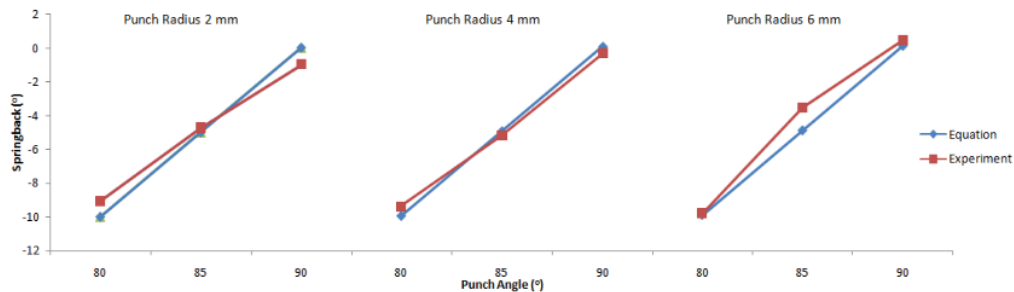


Fig. 2 Graph of spring back result

The spring back value for measured and calculated was shown in Fig. 2. The all of punch angles (80° , 85° and 90°) has a tendency to approach each other between which measured and calculated spring back.

Summary

Spring back has become an essential issue in the process of sheet metal forming. For investigating spring back, there have been numerous studies have been conducted and compared to theoretically spring back. It concluded that spring back can be predicted effectively and easily applied using the proposed analytical model, specifically for punch angle of 85° and 90° . Based on the analysis results could be predicted that the model gives good approval in accordance with experiments on a variety of different conditions.

References

- [1] Huang, Y.-M. and D.-K. Leu, Effects of process variables on V-die bending process of steel sheet. *International Journal of Mechanical Sciences*. 40(7) (1998), p. 631-650.
- [2] Slota, J., M. Jurčišin, and E. Spišák, Numerical and experimental springback determination of sheet metals in an air bending process. *Acta Metallurgica Slovaca*. 18(4) (2012), p. 200-209.
- [3] Chikalthankar, S., G. Belurkar, and V. Nandedkar, Factors Affecting on Springback in Sheet Metal Bending: A Review.
- [4] Kazan, R., M. Firat, and A.E. Tiryaki, Prediction of springback in wipe-bending process of sheet metal using neural network. *Materials & Design*. 30(2) (2009), p. 418-423.
- [5] Lange, K., *Handbook of metal forming*. 1985, New York: McGraw-Hill Company.
- [6] Mullan, H., Improved prediction of springback on final formed components. *Journal of Materials Processing Technology*. 153 (2004), p. 464-471.
- [7] Asnafi, N., Springback and fracture in v-die air bending of thick stainless steel sheets. *Material Design*. 21 (2000), p. 217-236.
- [8] Kalpakjian, S. and S.R. Schmid, *Manufacturing Processes for Engineering Materials*. 2008, New York: Persons Prentice Hall.
- [9] Damián-Noriega, Z., R. Pérez-Moreno, S. Villanueva-Pruneda, V. Domínguez-Hernández, J. Puerta-Huerta, and C. Huerta-Muñoz. A New Equation to Determine the Springback in the Bending Process of Metallic Sheet. in *ICCES: International Conference on Computational & Experimental Engineering and Sciences*. 2008.
- [10] Livatyali, H. and T. Altan, Prediction and elimination of springback in straight flanging using computer-aided design methods Part 1: experimental investigations. *Journal of Materials Processing Technology*. 117 (2001), p. 262-268.

The Influence of Punch Angle on the Spring Back during V-Bending of Medium Carbon Steel

ORIGINALITY REPORT

17%

SIMILARITY INDEX

12%

INTERNET SOURCES

10%

PUBLICATIONS

6%

STUDENT PAPERS

PRIMARY SOURCES

1	Submitted to Politeknik Negeri Bandung Student Paper	2%
2	journal.ubb.ac.id Internet Source	2%
3	jurnal.poliupg.ac.id Internet Source	2%
4	M A Suyuti, M Iswar, R Nur. "Effect of Punch Parameters on Springback for Mild Carbon Steel in A V-Shape Bending Process", IOP Conference Series: Materials Science and Engineering, 2019 Publication	1%
5	ijssbt.com Internet Source	1%
6	Adamou, Amadou, and Olisaemeka Osadebe. "Finite Element Analysis of Thin Rectangular Plate Subjected to Uniformly Distributed Transverse Load: A Java Application",	1%

International Journal of Engineering Research in Africa, 2015.

Publication

- | | | |
|----|---|-----|
| 7 | Submitted to Institute of Graduate Studies,
UiTM
Student Paper | 1 % |
| 8 | Submitted to Heriot-Watt University
Student Paper | 1 % |
| 9 | sciencepubco.com
Internet Source | 1 % |
| 10 | Hamid Baseri, Behzad Rahmani, Mohammad
Bakhshi-Jooybari. "PREDICTIVE MODELS OF
THE SPRING-BACK IN THE BENDING
PROCESS", Applied Artificial Intelligence, 2012
Publication | 1 % |
| 11 | Daw-Kwei Leu, Zhi-Wei Zhuang. "Springback
prediction of the vee bending process for
high-strength steel sheets", Journal of
Mechanical Science and Technology, 2016
Publication | 1 % |
| 12 | Jinwu, Wang, and Ma Tao. "Numerical
simulation of springback base on formability
index for auto panel surface", 2011
International Conference on Mechatronic
Science Electric Engineering and Computer
(MEC), 2011.
Publication | 1 % |
-

13	es.scribd.com Internet Source	1 %
14	sro.sussex.ac.uk Internet Source	1 %
15	Paweł Froń, Feliks Stachowicz. "SPRINGBACK CHARACTERISTICS OF THE TAILOR-WELDED 18G2A-E355 STEEL STRIPS", Acta Metallurgica Slovaca, 2013 Publication	<1 %
16	Sutasn Thipprakmas. "Chapter 10 Finite Element Analysis on V-Die Bending Process", IntechOpen, 2010 Publication	<1 %
17	Tilak Raj Gupta, Sarabjeet Singh Sidhu, Hoshiyar Singh Payal. "Effect of die width on spring back of electrogalvanized CR4 steel during air bending", Materials Today: Proceedings, 2018 Publication	<1 %

Exclude quotes Off
Exclude bibliography On

Exclude matches Off